

氏 名	こ ばり たつや
授 与 学 位	小 針 達 也
学 位 授 与 年 月 日	博士 (工学)
学位授与の根拠法規	平成27年3月25日
研究科, 専攻の名称	学位規則第4条第1項
学 位 論 文 題 目	東北大学大学院工学研究科 (博士課程) 機械システムデザイン工学専攻
	A Study of Heat Transfer in Thermal Insulation Materials
	and Its Precise Measurement
	(断熱材における伝熱現象とその高精度計測に関する研究)
指 導 教 員	東北大学教授 圓山 重直
論 文 審 査 委 員	主査 東北大学教授 湯上 浩雄 東北大学教授 小原 拓
	東北大学教授 塚田 隆夫 東北大学准教授 小宮 敦樹
	東北大学助教 岡島 淳之介

論 文 内 容 要 旨

Chapter 1: General introduction and background

In chapter 1, the general introduction and background of this study was described. The conventional and current thermal insulation materials were introduced. The investigations of theoretical and experimental study and the developments of thermal insulation materials were introduced. Consequently, the motivation and objectives of this dissertation was mentioned: the theoretical study of heat transfer in thermal insulation materials, the precise and accurate thermal conductivity measurement of thermal insulation materials, the radiative heat transfer analysis of vacuum insulation panels, and the development of vacuum insulation panel potentially capable of building materials.

Chapter 2: Fundamentals of heat transfer in insulation materials

In chapter 2, the fundamental of heat transfer in thermal insulation materials was explained. The heat transfer mechanisms and insulation performance of effective thermal conductivity, which can be separated into three contributions: solid thermal conductivity, gaseous thermal conductivity, and radiative thermal conductivity, were described.

Chapter 3: Analysis of effective thermal conductivity based on diffuse approximation

In chapter 3, three contributions to heat transfer in thermal insulation materials were discussed. The effective thermal conductivities of thermal insulation materials were theoretically separated into three contributions: solid thermal conductivity, gaseous thermal conductivity, and radiative thermal conductivity based on diffuse approximation. The theoretical separation was performed for various conventional insulation materials using literature data of their effective thermal conductivities. Figure 1 shows the Comparison among radiative, solid, and gaseous thermal conductivity of perlite separated from the literature data of effective thermal conductivity.

The reduction of radiative heat transfer is essential issue for the improvement of insulation performance of porous insulation materials. Comparing the Rosseland mean extinction coefficients obtained from temperature dependence of effective thermal conductivity based on diffuse approximation, the radiative heat transfer of porous insulation materials are quantitatively discussed. However, the anisotropic-scattering and non-gray radiation analysis, which can take account into the wavelength dependence, is necessary for the detailed investigation in wide range of temperature.

Chapter 4: Development of precise and accurate guarded hot plate apparatus using Peltier module

In chapter 4, a development of an accurate and precise measurement method for effective thermal conductivity of thermal insulation materials was performed. A guarded hot plate apparatus using a Peltier module was fabricated. A 2-D axisymmetric heat conduction analysis and calibration experiments for thermistor thermometers and Peltier module were conducted to develop the apparatus. Then, its accuracy and precision were discussed. The thermal conductivities of a high-density glass wool was measured as

a reference insulation material. The expanded uncertainties were estimated to discuss the precision. The 2-D axisymmetric heat conduction analysis based on the measurement condition for vacuum insulation panel specimen was conducted. The temperature distribution and heat loss were calculated to discuss the accuracy.

The Peltier module was sensitive enough to measure the temperature difference and eliminate the heat loss between the main plate and guard plate. Figure 2 shows a time variation of temperature difference in the Peltier module when the entire system was steady state. The use of the Peltier module achieved a temperature difference control with uncertainty of 20 μ K. The precision of the measurements by the apparatus was estimated. The expanded uncertainty of the thermal conductivity measurements was less than 5%. In particular, the expanded uncertainty for the thermal resistance measurement was 0.4%. The accuracy of the measurement by the apparatus was estimated from the heat loss. The bias error caused by the heat loss from the main plate to the guard plate was calculated as 0.13% for the vacuum insulation panel measurement condition. However, the accuracy also depends on the number and diameters of lead wires and the thickness of envelop of vacuum insulation panel.

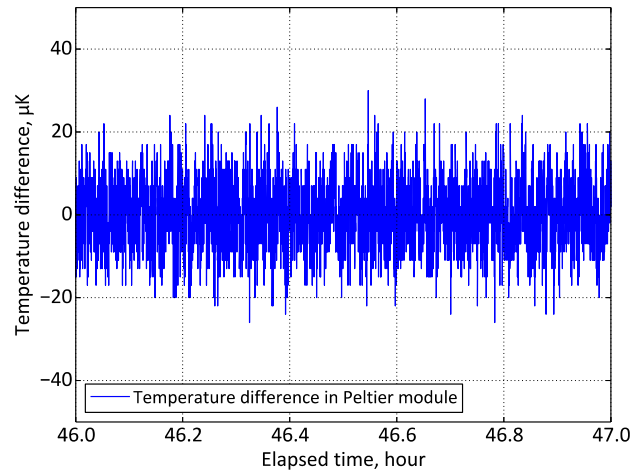


Fig. 2 Time variation of temperature difference in the Peltier module when the entire system was steady state.

Chapter 5: Measurement of effective thermal conductivity of vacuum insulation panels

In chapter 5, effective thermal conductivity measurements of commercial vacuum insulation panels were conducted using the developed guarded hot plate apparatus. The temperature dependence of effective thermal conductivity was measured. The solid thermal conductivity, radiative thermal conductivity, and gaseous thermal conductivity of the vacuum insulation panels were separately estimated based on diffuse approximation from the results.

The separate estimation indicated the effective thermal conductivities at 300 K of 3.34 mW/(m·K), 2.46 mW/(m·K), and 7.03 mW/(m·K), and the ratios of radiative thermal conductivities to effective thermal conductivities of 22%, 33%, and 25% at 300 K for the commercial vacuum insulation panel specimens A, B, and C, respectively. Figure 3 shows the measured effective thermal conductivities of one of the vacuum insulation panel specimens B and C against cube of average temperature with approximate line. This information contributes to improve the insulation performance of a vacuum insulation panel, and a reduction of radiative thermal conductivity achieves a development of vacuum insulation panel with a stable effective thermal conductivity against temperature condition. A radiation analysis based on not diffuse approximation but wavelength dependence has a grateful contribution to design a high-insulation performance vacuum insulation panel.

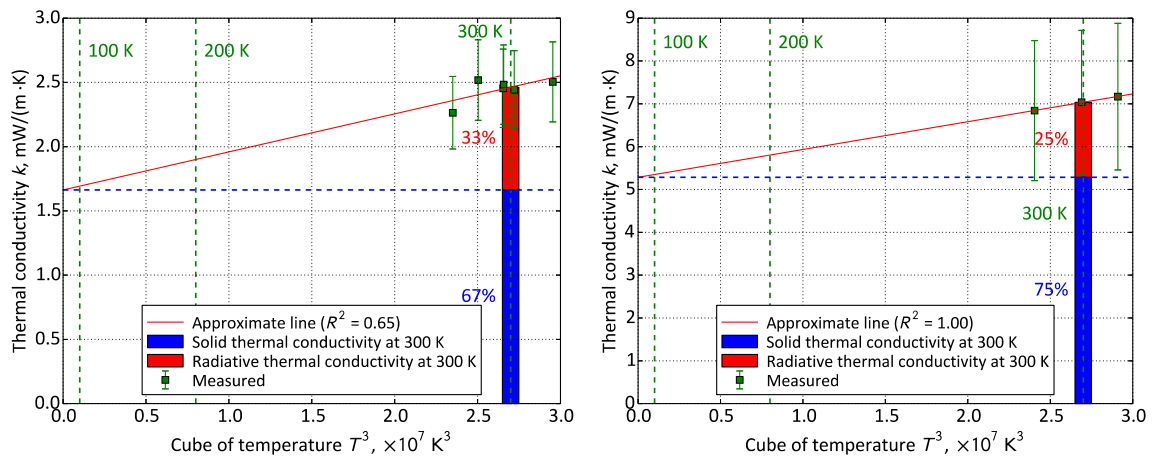


Fig. 3 Measured effective thermal conductivities of two vacuum insulation panel specimens B and C against cube of average temperature with approximate line.

Chapter 6: Development of vacuum insulation panel using expanded perlite

In chapter 6, a development of a vacuum insulation panel potentially capable for building material using expanded perlite was focused on. The design guide of VIP core material using expanded perlite was proposed based on a radiative heat transfer analysis using the radiation element method using ray emission model (REM²). The comparison between diffuse approximation and the radiation element method by ray emission model and the dependences of particle diameter and temperature condition were examined.

The database of extinction coefficient against the wavelength and particle diameter was made from the refractive index and used for the radiative analysis. The analysis results indicated that the radiative thermal conductivity is not proportional to the cube of temperature in contrast to the analysis based on diffuse approximation. The results suggested the preferred particle diameter for the temperature conditions: normal-temperature condition, high-temperature condition, and cryogenic condition. Figure 4 shows the analytical results of radiative thermal conductivity against the particle diameters for temperature condition of 77–300 K based on REM². It indicated that the design guide of vacuum insulation panels based on the radiation element method using ray emission model to realized the reduction of radiative thermal conductivity was established.

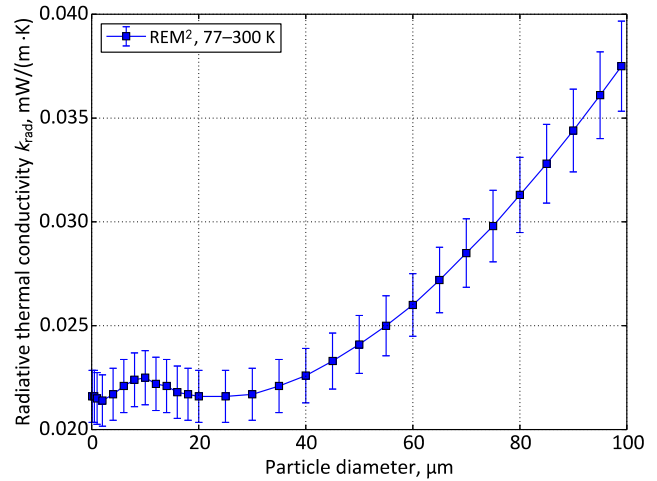


Fig. 4 Analytical results of radiative thermal conductivity against the particle diameters for temperature condition of 77–300 K based on REM².

Chapter 7: General conclusion

In chapter 7, the conclusions obtained from the each chapter were summarized, which will contribute to clarification of the heat transfer in insulation materials and design of insulation materials. The obtained conclusions were as follows.

1. The solid thermal conductivity, gaseous thermal conductivity, and radiative thermal conductivity were separately estimated and discussed from the temperature dependence of effective thermal conductivity for various porous insulation materials based on diffuse approximation.
2. An accurate and precise guarded hot plate method was development for measurement of effective thermal conductivity of thermal insulation materials.
3. Using developed guarded hot plate method, effective thermal conductivity of commercial vacuum insulation panels was measured and discussed.
4. Design method for vacuum insulation panel with core material of perlite, which has high thermal insulation performance and low cost, was made based on radiative heat transfer analysis.

論文審査結果の要旨

材料や構造、環境に依存する断熱材の伝熱現象を理解し断熱性能を向上させることは、環境面、経済面上の問題において重要となる。断熱という基盤技術において断熱性能の向上は重要な課題であり、内部の伝熱現象の詳細な把握が必要となる。本研究では断熱材の伝熱現象の理解を深め断熱性能の高精度計測を行い、断熱性能向上に向けた解析を行っている。本論文は、これらの研究成果をまとめたものであり、全編 7 章からなる。

第 1 章は序論であり、本研究の背景、目的および構成を述べている。

第 2 章では、断熱材における伝熱現象の理論を述べている。有効熱伝導率という見掛けの熱物性を導入し、これに寄与する伝熱現象として伝導伝熱、対流熱伝達、ふく射伝熱について議論している。この議論は次章以降において重要な知見である。

第 3 章では、種々の多孔質断熱材について、有効熱伝導率の温度依存性の測定データの文献値を用い、有効熱伝導率を構成する固体熱伝導率、気体熱伝導率、ふく射熱伝導率に分離して評価している。その結果、それぞれの断熱材においてどの伝熱現象が支配的であることを明らかにしている。これは、断熱材の設計指針を考える上で有効及び重要な成果である。

第 4 章では、ペルチェモジュールを用いた保護熱板法による断熱材の高精度な有効熱伝導率測定手法を確立している。また、提案した手法が高い確度と精度を実現していることを評価している。これは、断熱材の断熱性能評価のために有効かつ重要な成果である。

第 5 章では、第 4 章で確立した測定手法により、高性能断熱材である真空断熱パネルの微小な有効熱伝導率の温度依存性の測定をしている。結果から第 3 章で行った評価を適用し、使用した真空断熱パネルにおいてどの伝熱現象が支配的かを明らかにしている。これは、真空断熱パネルの断熱性能向上のために重要な知見である。

第 6 章では、パーライトを芯材に使用した真空断熱パネルを提案しそのふく射伝熱解析を行っている。パーライト粉末による散乱性や波長依存性を考慮したふく射解析を行うことで、最適となる粒径の設計指針の提案をしている。これは、実用化に向けた重要な成果である。

第 7 章は結論である。

以上要するに本論文は、断熱材の伝熱現象を高精度に計測することでその理解を深め、ふく射伝熱制御に基づいた断熱性能の向上を行ったものであり、機械システムデザイン工学および伝熱工学の発展に寄与するところが少なくない。

よって、本論文は博士(工学)の学位論文として合格と認める。